

GUARNIFLON S.p.A. - PATI Division

Product code : 0TQHST9900 - 150 mic

Direction : TD

Preload : 0,05 MPa


Rate of grip separation : 500 mm/min

Initial grip separation : 50,00 mm

Risultati del test:

Sample no.	Thickness μm	S_0 mm^2	E_t 0.1% MPa	Stress 10% MPa	Tensile strength at break MPa	Tensile strain at break %
1	148	1,48	927	22,1	57,6	380
2	148	1,48	920	21,6	52,0	360
3	150	1,50	928	22,0	56,4	380
4	150	1,50	903	21,7	52,0	360

Grafico della serie:

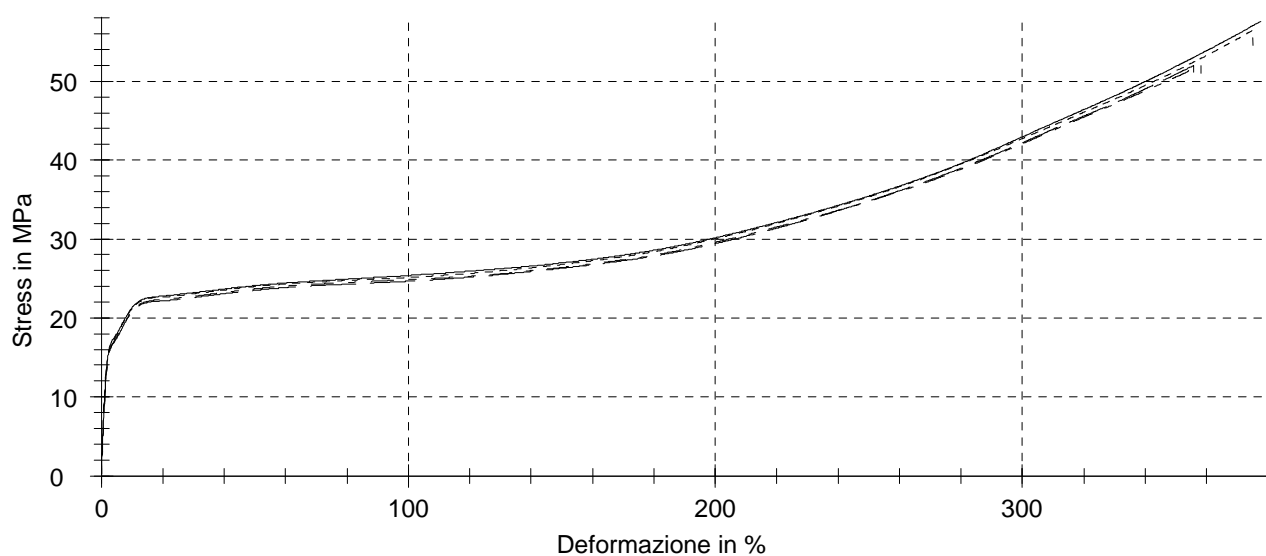

Statistiche:

Serie	Thickness μm	S_0 mm^2	E_t 0.1% MPa	Stress 10% MPa	Tensile strength at break MPa	Tensile strain at break %
n = 4						
\bar{x}	149	1,49	920	21,8	54,5	370